


NASA TECH BRIEF



NASA Tech Briefs are issued to summarize specific innovations derived from the U.S. space program, to encourage their commercial application. Copies are available to the public at 15 cents each from the Clearinghouse for Federal Scientific and Technical Information, Springfield, Virginia 22151.

Application of the Solid Lubricant Molybdenum Disulfide by Sputtering

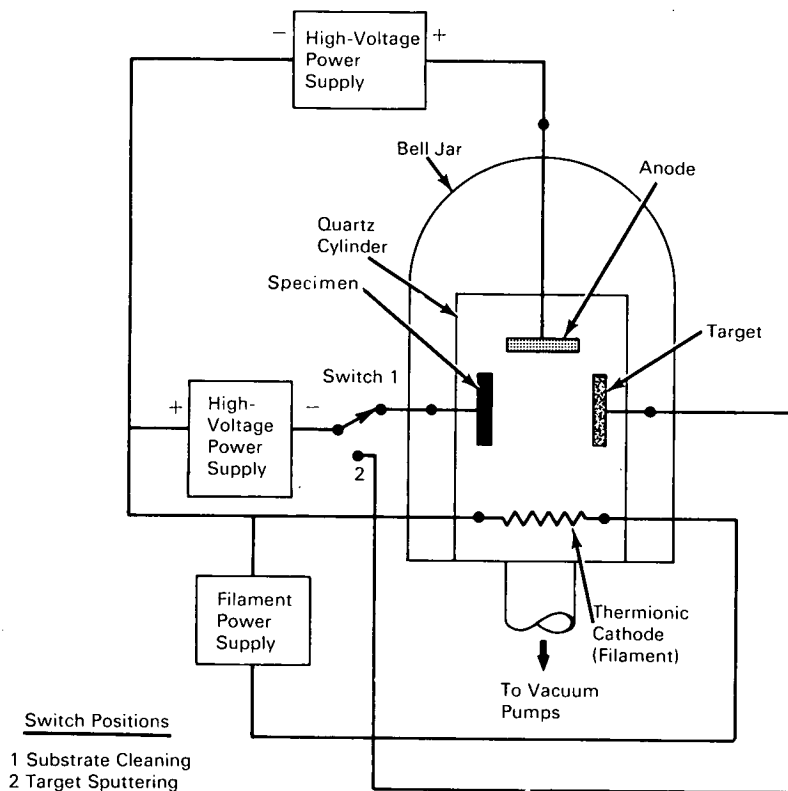

The problem:

Molybdenum disulfide (MoS_2) is frequently used as a solid lubricant in conventional and in high-temperature and high-vacuum environments. To be durable and effective, lubricant films of MoS_2 must be firmly bonded to the surface of the material requiring lubrication. Obtaining uniform, strongly bonded films has been a limiting problem.

Previously, MoS_2 films have been obtained either by using binders or by burnishing the substrate material with MoS_2 powder. There are applications where a bonding agent is undesirable, as for example, environments producing chemical interactions that affect film adherence through decomposition of the binder. Burnished MoS_2 films have relatively poor bonding and usually have a higher coefficient of friction and poor coating thickness uniformity.

(continued overleaf)

The solution:

A molybdenum disulfide lubricant film was deposited under controlled experimental conditions on two substrates, niobium (Nb) and nickel-chromium (Ni-Cr) alloys, by means of physical direct-current sputtering.

How it's done:

The sputtering system uses a three-electrode (triode) geometry: a thermionic cathode, an anode, and the target, all enclosed in a vacuum chamber.

The thermionic cathode is a spiraled filament of 1 millimeter-thick tungsten wire which, when heated, acts as a thermionic electron source. The anode is a flat stainless steel disk to which a positive electrical potential of about 500 volts is applied to establish a flow discharge between it and the thermionic cathode. The target (the material to be deposited) is a cylindrically shaped binder-free compact of MoS₂, 1.3 cm in diameter and about 5 cm long, held in a water cooled holder. A negative electrical potential is applied to this target.

The substrate material (Nb and a Ni-Cr alloy disk) is placed close to the target material and the atoms ejected from the target are deposited on the substrate to form a continuous film which is both uniform and strongly adherent. Thicknesses of the films were measured during and after sputtering and were in the range of 2000- to 3000-angstroms.

Notes:

1. Measured coefficients of friction of the sputtered MoS₂ film (0.06 to 0.09) are in agreement with the values (0.03 to 0.08) reported in the literature for resin-bonded films.
2. The sputtered MoS₂ lubricant film on the niobium substrate was friction tested for more than five hours without failure in ultrahigh vacuum at loads of 250 grams and a speed of 5 ft/min. This lubricating film durability gives a qualitative test of the strong bonding adherence between film and substrate. The film thickness was uniform, and film thickness repeatability was maintained.
3. The MoS₂ cylindrical compact was made without a binder by using compacting pressures of 50,000 to 100,000 psi.
4. Inquiries concerning this innovation may be directed to:

Technology Utilization Officer
Lewis Research Center
21000 Brookpark Road
Cleveland, Ohio 44135
Reference: B68-10340

Patent status:

No patent action is contemplated by NASA.

Source: T. Spalvins and J. Przybyszewski
(LEW-10544)